

Thermodynamic and magnetic properties of the layered triangular magnet NaNiO_2

P. J. Baker,¹ T. Lancaster,¹ S. J. Blundell,¹ M. L. Brooks,¹ W. Hayes,¹ D. Prabhakaran,¹ and F. L. Pratt²

¹*Clarendon Laboratory, University of Oxford, Parks Road, Oxford OX1 3PU, United Kingdom*

²*ISIS Muon Facility, ISIS, Chilton, Oxon. OX11 0QX, United Kingdom*

(Dated: February 2, 2008)

We report muon-spin rotation, heat capacity, magnetization, and ac magnetic susceptibility measurements of the magnetic properties of the layered spin-1/2 antiferromagnet NaNiO_2 . These show the onset of long-range magnetic order below $T_N = 19.5$ K. Rapid muon depolarization, persisting from T_N to about 5 K above T_N , is consistent with the presence of short-range magnetic order. The temperature and frequency dependence of the ac susceptibility suggests that magnetic clusters persist above 25 K and that their volume fraction decreases with increasing temperature. A frequency dependent peak in the ac magnetic susceptibility at $T_{sf} = 3$ K is observed, consistent with a slowing of spin fluctuations at this temperature. A partial magnetic phase diagram is deduced.

PACS numbers: 76.75.+i, 75.50.Ee, 75.30.Gw

Geometrically frustrated transition metal oxides exhibit a rich variety of magnetic behavior due to competing interactions. A significant degeneracy in the ground state leads to such phenomena as spin glass¹, spin liquid², and spin ice³ phases. Triangular lattice antiferromagnets exhibit a variety of these phenomena⁴. When the triangles forming the lattice are distorted from equilateral to isosceles there is a partial release of the geometrical frustration, which can lead to more unusual forms of magnetic order^{5,6,7}. Among triangular lattice antiferromagnets, LiNiO_2 ⁸, AgNiO_2 ⁹, and NaNiO_2 have somewhat enigmatic magnetic behavior. The difficulty of producing stoichiometric LiNiO_2 has led to a variety of sample-dependent results¹⁰. AgNiO_2 can be produced in stoichiometric form but no magnetic Bragg peaks have so far been reported⁹. Recently neutron powder diffraction studies have determined the low temperature magnetic structure of NaNiO_2 ^{11,12}. Darie et al.¹¹ find the ordering of the magnetic moments at 4 K to be a slight modification of the A-type antiferromagnetic ordering previously proposed¹³. The magnetic moments were found to be aligned at an angle of $100(2)^\circ$ to the a -axis in the ac plane with no moment along the b -axis. A peak in the magnetic susceptibility interpreted as the Néel temperature, T_N , has been observed around 20 K^{13,14,15}. The Curie-Weiss constant, $\theta_{CW} = +36$ K¹⁵, shows the presence of ferromagnetic interactions above T_N .

The intralayer and interlayer exchange constants of NaNiO_2 , $J_{||} = -13.3$ K and $J_{\perp} = 1.3$ K, were determined from a model assuming an A-type antiferromagnetic ordering with an anisotropy field¹⁶; the layers are sufficiently strongly coupled to permit long range magnetic order below T_N . The Ni-O-Ni bond angles are $\approx 95^\circ$ at room temperature¹⁷. An undistorted 90° geometry favours weak ferromagnetic superexchange, while a large deviation from a 90° bond angle can reverse the sign of this exchange coupling¹⁸. In NaNiO_2 it appears that despite the distortion, in-plane ferromagnetic coupling prevails, though the precise nature of the spin and orbital ordering remains under discussion^{19,20,21}.

Above 480 K the space group of NaNiO_2 is rhombohe-

dral ($R\bar{3}m$) and there is a cooperative Jahn-Teller transition to a low temperature monoclinic ($C2/m$) phase below this temperature¹⁷. The low-temperature structure can be considered to be layers of NiO_6 octahedra in the ab plane, with a trigonal distortion lengthening the Ni-O bonds in the ac plane along an axis at 41° to the c -axis of the crystal. The Ni^{3+} ($3d^7$) ion is in the low spin state ($t_{2g}^6 e_g^1$, $S = 1/2$), so the ground state is a singly-occupied $|3z^2 - r^2\rangle$ orbital with z along the axis of the Jahn-Teller induced trigonal distortion¹⁷.

In this paper we present the results of zero-field muon spin rotation (μSR) experiments²² on polycrystalline NaNiO_2 together with heat capacity and magnetic susceptibility measurements. These provide evidence of long range magnetic order below T_N , a slowing of spin fluctuations at low temperature, and short range magnetic order within a small temperature region above T_N , with magnetic correlations persisting to higher temperature.

NaNiO_2 was prepared from Na_2O_2 and NiO powders heated at 700°C for 100 hours under pure oxygen flow, with intermediate grinding. X-ray powder diffraction showed that the impurity concentration was below the 2% resolution limit of the apparatus. Heat capacity data measured in magnetic fields between 0 and 14 T, taken with a Quantum Design PPMS, are shown in Fig. 1(a). In zero field the transition at $T_N = 19.5$ K is seen as a rather broad peak, and there is no evidence for other phase transitions below 30 K. With increasing magnetic field the temperature of this peak decreases to about 14 K (see Fig. 1(a)).

Magnetic susceptibility data, taken using a Quantum Design MPMS SQUID magnetometer are shown in Fig. 1(b), (d) and (e). The high temperature dc susceptibility data, shown in Fig. 1(e), are consistent with $\theta_{CW} = +36$ K¹⁵. The real and imaginary parts of the ac susceptibility, χ' and χ'' , are presented in Figs. 1(b) and (d) (driving field 3.5 Oe). They show a frequency dependent peak in χ' located slightly above a spin-freezing temperature T_{sf} , which is determined below. Figure 1(d) shows the temperature variation of this peak in χ' with frequency. It was found that this could be fitted to the

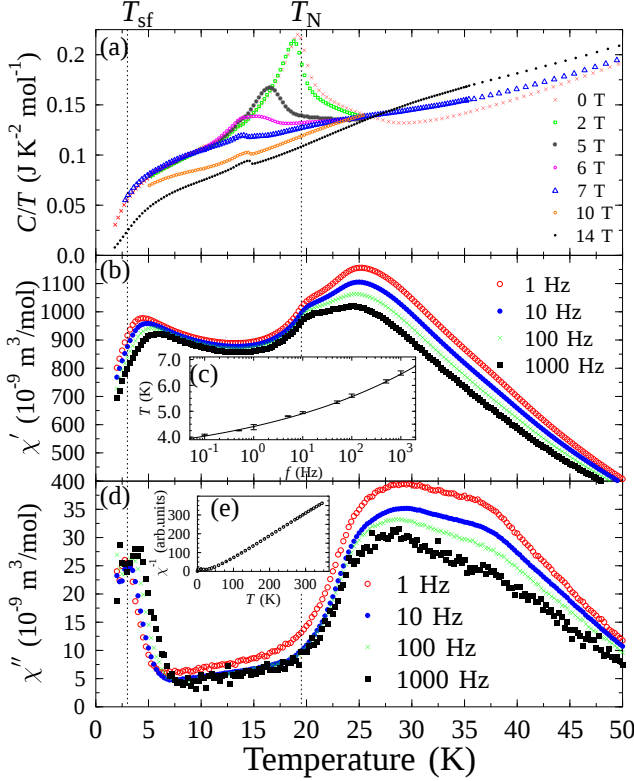


FIG. 1: (Color online) The panels correspond to: (a) Heat capacity divided by temperature in fields between 0 and 14 T. (b) Real part, χ' , of the ac magnetic susceptibility. (c) Temperature dependence of the peak in χ' associated with T_f with a fit to the Ogielski relation (Eq. (1)). (d) Imaginary part, χ'' , of the ac magnetic susceptibility. (e) Inverse of magnetic susceptibility data against temperature with a linear fit showing the high-temperature Curie-Weiss behavior. The vertical dashed lines indicate temperatures referred to in the text.

Ogielski scaling relation²³:

$$T = T_{sf}(1 + (f\tau_0)^{1/z\nu_c}), \quad (1)$$

where T is the temperature of the peak in χ' , f is the measurement frequency, τ_0 is the relaxation time of the system, z is a dynamic exponent, and ν_c is a critical exponent. Fitting the data to Eq. (1) gives $T_{sf} = 3 \pm 0.2$ K, $\tau_0 = 5.4(2) \times 10^{-3}$ s and $z\nu_c = 8.1 \pm 0.4$. This is typical of glassy behavior or the slowing of spin fluctuations. Given that muon precession was observed down to 1.6 K (see below), the formation of a true spin glass around T_{sf} is excluded. One possible interpretation of the feature around T_{sf} is that it could arise from a small concentration of defects comprised of pairs of Ni^{2+} impurity spins which are associated with oxygen vacancies. Alternatively, the fluctuations in the spins could be slowing down around T_{sf} . At T_N , χ' has a small maximum and rises to a larger peak near 25 K, with the frequency dependence increasing from T_N to the peak, and decreasing above it. The temperature of the peak in χ' at 25 K decreases slowly with increasing frequency, which may

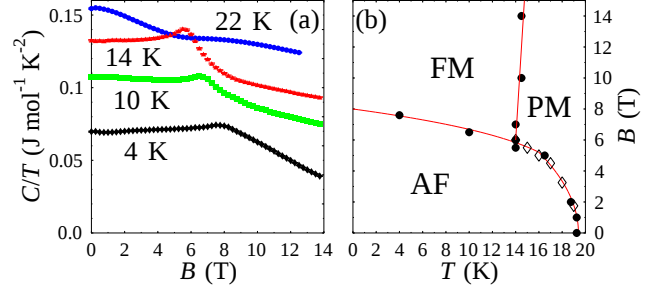


FIG. 2: (Color online) (a) Heat capacity divided by temperature vs field at four temperatures. (b) Partial magnetic phase diagram deduced from heat capacity ($\bullet$) and magnetization ($\diamond$) data. AF: A-type antiferromagnetic phase. PM: Paramagnetic phase. FM: Ferromagnetic phase.

be related to the presence of two sets of relaxation times varying differently with temperature (see below). χ'' also rises sharply near 25 K but to a plateau continuing up to ~ 35 K. Together these suggest that short-range order persists up to ~ 25 K, that slowly fluctuating clusters of spins are present within a fast fluctuating paramagnetic bulk above this temperature, and that the volume fraction of clusters decreases with increasing temperature.

Constant temperature heat capacity data with varying magnetic field are presented in Fig. 2(a). Except for the data taken at 22 K, a peak is observed which corresponds to the field labelled H_{C1} in the magnetization data reported in Ref. 16. This suggests that this marks the upper field boundary of A-type antiferromagnetic order. At 22 K the heat capacity decreases with increasing field consistent with short-range order. The partial magnetic phase diagram deduced from our heat capacity and magnetization data is shown in Fig. 2(b).

Our zero-field μ SR experiments were carried out using the DOLLY instrument at the Paul Scherrer Institute (PSI), Villigen, Switzerland. In our μ SR experiments, spin polarized positive muons (μ^+ , mean lifetime 2.2 μ s, momentum 28 MeV/c) were implanted into polycrystalline NaNiO_2 . The decay positron asymmetry function, $A(t)$ ²², is proportional to the average spin polarization of the muons stopped within the sample. The muon spin precesses around an internal magnetic field, B_μ , at a frequency $\nu_\mu = (\gamma_\mu/2\pi)|B_\mu|$, where $\gamma_\mu/2\pi = 135.5$ MHz T^{-1} .

The asymmetry data were fitted to Eq. (2)²⁴ below T_N , and to Eq. (3) above T_N :

$$A(t) = A(0) (P_1 e^{-\lambda_1 t} + P_2 e^{-\lambda_2 t} \cos(2\pi\nu_\mu t + \phi_0)) \quad (2)$$

$$A(t) = A(0) (P_f e^{-\lambda_f t} + P_s e^{-\lambda_s t}), \quad (3)$$

where $A(0)$ is the initial asymmetry. P_1 and P_2 are respectively the longitudinal and transverse components of the muon polarization, and $P_1 + P_2 = 1$. The exponential relaxation associated with P_1 reflects the dynamical fluctuations of the fields being probed. The P_2 term describes muon precession with a distribution of local fields

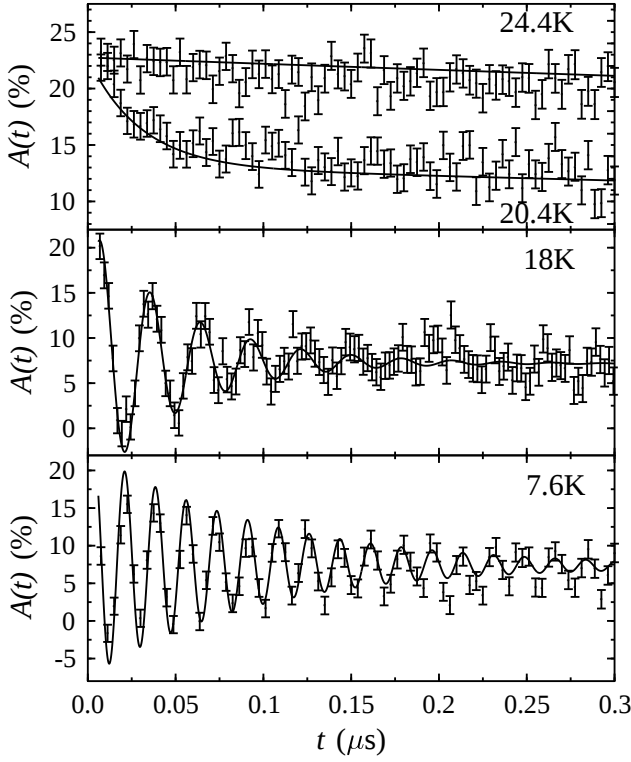


FIG. 3: Muon decay asymmetry in NaNiO_2 plotted at different temperatures. The solid lines are fits of the data to Eqs. (2) & (3) with the parameters shown in Fig. 4.

dephasing the muon spins. In a fully magnetically ordered polycrystalline sample we expect $P_2/P_1 = 2$. Coherent muon precession will be observed if long range order is present within the sample. P_s and P_f describe slow and fast dynamic fluctuations respectively. A small initial phase offset, ϕ_0 , was observed below T_N , larger than could be attributed to errors in determining the time that the muons enter the sample. This could be produced by a small magnetic inequivalency in the position of muons stopped within the sample, consistent with an asymmetric peak seen in Fourier transforms of the data. In the fitting procedure, data were fitted in the time range $0 < t < 8 \mu\text{s}$, where the effect of background counts could be reliably subtracted. Rapid dynamic fluctuations lead to $\lambda_1 \propto \gamma_\mu^2 (\Delta B)^2 / \nu$, where ΔB is the amplitude of the fluctuating local field and ν is the fluctuation rate²⁴.

Spectra measured at four temperatures are shown in Fig. 3. There are three distinct temperature regions apparent from the muon asymmetry spectra. At low temperatures ($T \leq 19.5 \text{ K}$) there are clear oscillations in the asymmetry showing that long range magnetic order exists and the observed ratio of $P_2 : P_1 \approx 2$ (see Fig. 4(b)) indicates that the sample is magnetic over its entire volume. The value of $\lambda_{2,s}$ is much larger than $\lambda_{1,f}$ (see Fig. 4(c) & (d)) so at short times only the effect of $\lambda_{2,s}$ is seen in Fig. 3. An intermediate temperature range ($19.5 < T < 24 \text{ K}$) gives no oscillations, and the relax-

ation is modelled with the two exponential components of Eq. (3), with the amplitude of the faster relaxing component decreasing with increasing temperature. Above 24 K the relaxation is well described by a single exponential, $P \exp(-\lambda_f t)$, consistent with fast fluctuations of paramagnetic moments characterized by a single correlation time in the muon time window.

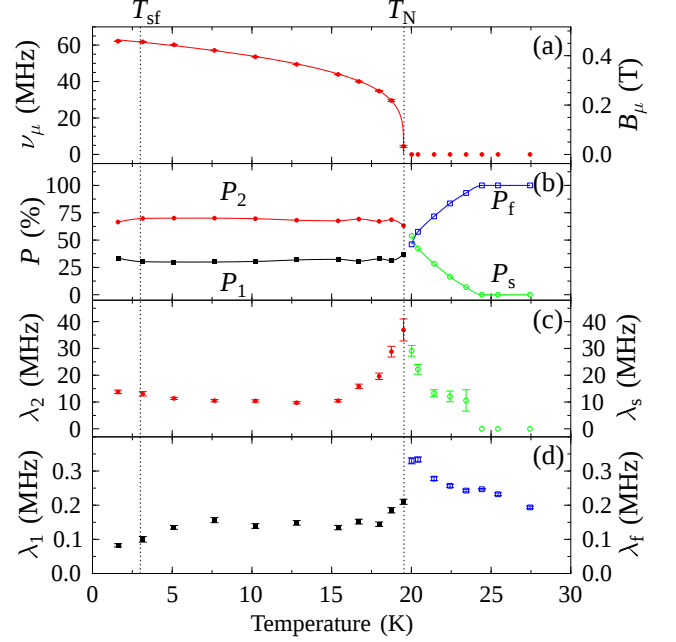


FIG. 4: (Color online) Temperature dependence of the parameters determined from fitting data to Eqs. (2) & (3): (a) the oscillation frequency, ν_μ , and the internal magnetic field, B_μ , with a fit to Eq. (4). (b) Amplitudes of the relaxation components P_1 and P_2 , and P_f and P_s . (c) Relaxation rates λ_2 and λ_s . (d) Relaxation rates λ_1 and λ_f . The vertical dashed lines indicate temperatures referred to in the text.

The temperature dependence of the parameters derived from fitting Eqs. (2) & (3) to muon asymmetry spectra are presented in Fig. 4. The muon precession frequency, ν_μ , in the ordered phase is shown in Fig. 4(a). This is proportional to the sublattice magnetization at the muon site, and was fitted to a function²⁵:

$$\nu_\mu(T) = \nu_\mu(0)(1 - (T/T_N))^{\beta_m}. \quad (4)$$

The fit gives $\nu_\mu(0) = 64.2(2) \text{ MHz}$ corresponding to a field at the muon site of $\sim 0.5 \text{ T}$. Dipole field calculations show that this field will be experienced by muons near any of the oxygen atoms in the octahedron surrounding a nickel atom, in regions of high electron density²⁶, and show that our results are consistent with the magnetic structure determined by Darie et al.¹¹. Our calculations also suggest that the muon precession frequency is insensitive to small deviations from this magnetic structure. Fitting Eq. (4) to the muon precession frequencies gave $T_N = 19.51(1) \text{ K}$ and $\beta_m = 0.24(1)$. This value of β_m suggests that the system is behaving as a 2D XY magnet²⁷.

In relation to the peak just above T_{sf} in the magnetic susceptibility, we note that extrapolating the Ogielski scaling relation to the muon time window suggests a maximum in the dynamic relaxation rate λ_1 should be observed around 7 K, and a broad maximum of low amplitude is just detectable at this temperature (Fig. 4(d)). The presence of two exponential relaxation components above T_N (see Eq. (3)) suggests that short-range magnetic order persists over a small temperature range of ~ 5 K above T_N . The fluctuations in the magnetic field producing the faster relaxing component, λ_s , are two orders of magnitude slower than those producing the slowly relaxing component, λ_f . P_s decreases with increasing temperature up to 24 K, showing that the ratio of slow to fast dynamic relaxation is decreasing. Above this temperature the muon relaxation is that expected for a system in the fast-fluctuation regime. The slow spin relaxations observed in the frequency dependence of the ac susceptibility above 25 K are not within the muon time window so are not observed. The observation of two components in the muon relaxation below 24 K, together with a changing frequency dependence of the ac susceptibility, suggest a model of coalescing magnetic clusters forming well above T_N . On cooling below ~ 50 K, these magnetic clusters occupy an increasing volume fraction, causing the increase in the frequency dependence of the ac susceptibility, until at ~ 25 K the sample possesses

short-range antiferromagnetic order. Below 25 K these clusters coalesce, leading to the decrease in the frequency dependence of the ac susceptibility, and the increase in P_s , until at T_N the sample possesses long-range order. Short-range order within the layers and antiferromagnetically correlated layers is consistent with the persistence of unbroadened magnetic Bragg peaks observed by neutron powder diffraction over a similar temperature range above T_N ^{12,28}.

In conclusion, NaNiO_2 shows the onset of long-range magnetic order at $T_N = 19.5$ K, with the dependence of the sublattice magnetization on temperature appropriate for a 2D XY magnet. The slowing of spin fluctuations above T_{sf} is evident in the ac magnetic susceptibility data. At temperatures just above T_N there is evidence of short-range order, and of magnetic clusters persisting within a paramagnetic phase above this temperature.

Part of this work was performed at the Swiss Muon Source, Paul Scherrer Institute, Villigen, Switzerland. We are grateful to Robert Scheuermann for experimental assistance, and to M. Holzapfel, B. D. Gaulin, and A. Coldea for helpful discussions. T. L. acknowledges support from the European Commission under the 6th Framework Programme through the Key Action: Strengthening the European Research Area, Research Infrastructures. Contract no: RII3-CT2003-505925. This work was funded by the EPSRC (UK).

-
- ¹ J. S. Gardner, B. D. Gaulin, S.-H. Lee, C. Broholm, N. P. Raju, and J. E. Greedan, *Phys. Rev. Lett.* **83**, 211 (1999).
 - ² F. Mila, *Eur. J. Phys.* **21**, 499 (2000).
 - ³ J. Snyder, J. S. Slusky, R. J. Cava, and P. Schiffer, *Nature* **413**, 48 (2001).
 - ⁴ M. F. Collins and O. A. Petrenko, *Can. J. Phys.* **75**, 605 (1997).
 - ⁵ R. Coldea, D. A. Tennant, and Z. Tylczynski, *Phys. Rev. B* **68**, 134424 (2003).
 - ⁶ S. Kobayashi, S. Mitsuda, M. Ishikawa, K. Miyatani, and K. Kohn, *Phys. Rev. B* **60**, 3331 (1999).
 - ⁷ B. C. Sales, R. Jin, K. A. Affholter, P. Khalifah, G. M. Veith, and D. Mandrus, *Phys. Rev. B* **70**, 174419 (2004).
 - ⁸ T. Chatterji, W. Henggeler, and C. Delmas, *J. Phys. Condens. Matter* **17**, 1341 (2005).
 - ⁹ H. Kikuchi, H. Nagasawa, M. Mekata, Y. Fudamoto, K. M. Kojima, G. M. Luke, Y. J. Uemura, H. Mamiya, and T. Naka, *Hyperfine Interact.* **120-121**, 623 (1999).
 - ¹⁰ M. D. Núñez-Regueiro, E. Chappel, G. Chouteau, and C. Delmas, *Eur. Phys. J. B* **16**, 37 (2000).
 - ¹¹ C. Darie, P. Bordet, S. de Brion, M. Holzapfel, O. Isnard, A. Lecchi, J. E. Lorenzo, and E. Suard, *Eur. Phys. J. B* **43**, 159 (2005).
 - ¹² M. J. Lewis, B. D. Gaulin, L. Filion, C. Kallin, A. J. Berlinsky, H. A. Dabkowska, Y. Qiu, and J. R. D. Copley, (unpublished), cond-mat/0409727.
 - ¹³ P. F. Bongers and U. Enz, *Solid State Commun.* **4**, 153 (1966).
 - ¹⁴ J. P. Kemp, P. A. Cox, and J. W. Hodby, *J. Phys. Condens. Matter* **2**, 6699 (1990).
 - ¹⁵ E. Chappel, M. D. Núñez-Regueiro, F. Dupont, G. Chouteau, C. Darie, and A. Sulpice, *Eur. Phys. J. B* **17**, 609 (2000).
 - ¹⁶ M. Holzapfel, S. de Brion, C. Darie, P. Bordet, E. Chappel, G. Chouteau, P. Strobel, A. Sulpice, and M. D. Núñez-Regueiro, *Phys. Rev. B* **70**, 132410 (2004).
 - ¹⁷ E. Chappel, M. D. Núñez-Regueiro, G. Chouteau, O. Isnard, and C. Darie, *Eur. Phys. J. B* **17**, 615 (2000).
 - ¹⁸ S. Tornow, O. Entin-Wohlman, and A. Aharony, *Phys. Rev. B* **60**, 10206 (1999).
 - ¹⁹ A.-M. Daré, R. Hayn, and J.-L. Richard, *Europhys. Lett.* **61**, 803 (2003).
 - ²⁰ F. Vernay, K. Penc, P. Fazekas, and F. Mila, *Phys. Rev. B* **70**, 014428 (2004).
 - ²¹ A. J. W. Reitsma, L. F. Feiner, and A. M. Oleś, *New J. Phys.* **7**, 121 (2005).
 - ²² S. J. Blundell, *Contemp. Phys.* **40**, 175 (1999).
 - ²³ A. T. Ogielski, *Phys. Rev. B* **32**, 7384 (1985).
 - ²⁴ P. Dalmás de Réotier and A. Yaouanc, *J. Phys. Condens. Matter* **9**, 9113 (1997).
 - ²⁵ F. Borsa, P. Carreta, J. H. Cho, F. C. Chou, Q. Hu, D. C. Johnston, A. Lascialfari, D. R. Torgeson, R. J. Gooding, N. M. Salem, et al., *Phys. Rev. B* **52**, 7334 (1995).
 - ²⁶ H. Meskine and S. Satpathy, *J. Appl. Phys.* **97**, 10A314 (2005).
 - ²⁷ S. T. Bramwell, P. C. W. Holdsworth, and M. T. Hutchings, *J. Phys. Soc. Jpn.* **64**, 3066 (1995).
 - ²⁸ B. D. Gaulin, (private communication).